

UDC 577.11

I. Rau, F. Kajzar, G. Zaikov,  
Kh. Abzalidinov

# BIOPOLYMERS FOR APPLICATION IN PHOTONICS. PART 1

**Keywords:** Deoxyribonucleic acid, DNA, collagen, DNA-CTMA complex, linear optical properties, nonlinear optical properties, photoluminescence, photo-thermal stability, optical damage threshold, thin films.

*Possibilities of utilization of biopolymers, and particularly of the deoxyribonucleic acid (DNA) are reviewed and discussed. The ways of their functionalization with photoresponsive molecules to get desired properties are described and illustrated on several examples as well as the processing of materials into thin films. Their room - and photo-thermal stability, studied by spectroscopic techniques is reported, together with optical damage thresholds. Physical properties, and more particularly linear, nonlinear and photoluminescent properties of obtained materials are also reviewed and discussed.*

**Ключевые слова:** дезоксирибонуклеиновая кислота, ДНК, коллаген, комплекс ДНК-СТМА, линейные оптические свойства, нелинейные оптические свойства, фотолюминесценция, фототермическая стабильность, порог оптического разрушения, тонкие пленки.

*Рассматриваются и обсуждаются возможности использования биополимеров, и в частности дезоксирибонуклеиновой кислоты (ДНК). На нескольких примерах дается описание способов их функционализации фоточувствительными молекулами для получения желаемых свойств, а также при переработке материалов в тонкие пленки. Спектроскопическими методами изучена стабильность при комнатных условиях, фототермическая стабильность, а также пороги оптических разрушений. Также рассматриваются и обсуждаются физические свойства, и, в частности, линейные, нелинейные и фотолюминесцентные свойства полученных материалов.*


## 1. Introduction

In last 30 years time the synthetic polymers have found large applications in almost each domain of human activity, and particularly in construction, car industry, medicine, textile and more recently in advanced technologies. These polymers are obtained principally from coal and from oil by chemical transformation and synthesis. However, due to the fact that the coal and oil resources are limited on one hand and contribute to an important pollution of the planet on the other the scientists turns their attention to nature produced biopolymers. Indeed, the decay time for a thin foil of polyethylene (PET), used largely in fabrication of plastic bottles, is of 5 – 10 years. Also the largely used polystyrene (PS) decomposes in 50 years, low-density polyethylene (LDPE) in 500 – 1000 years. Polypropylene (PP), used in clothing and rope fabrication, practically does not degrade [1]. The fabrication of some polymers, like polyvinyl chloride (PVC), used largely in construction and in fabrication of toys is done with the use of toxic dioxin. Its degradation is associated with the production of unhealthy subproducts. These facts explain well the already mentioned switch of the scientists interest to natural biopolymers, originating from renewable resources and biodegradable.


One of these polymers which attracted recently some interest is chitosan which is a polysaccharide, occurring in the exoskeleton of invertebrates and in their internal structures. It was shown that it has some interesting optical properties [2, 3]. There are two biopolymers produced in a very large amount by nature which are the deoxyribonucleic acid (DNA) and

collagen. Both are biodegradable, abundant and can be obtained from, e.g., the waste of food producing industry.


DNA, called also “molecule of live”, is present in all living species, being responsible for its development and heritage not only of humans and animals but also of the vegetal ones. Since the discovery of its molecular structure by Watson and Crick [4, 5] (cf. Figure 1) in 1953 the deoxyribonucleic acid (DNA) attracted a lot of interest of biologists, chemists, and later, of physicists.

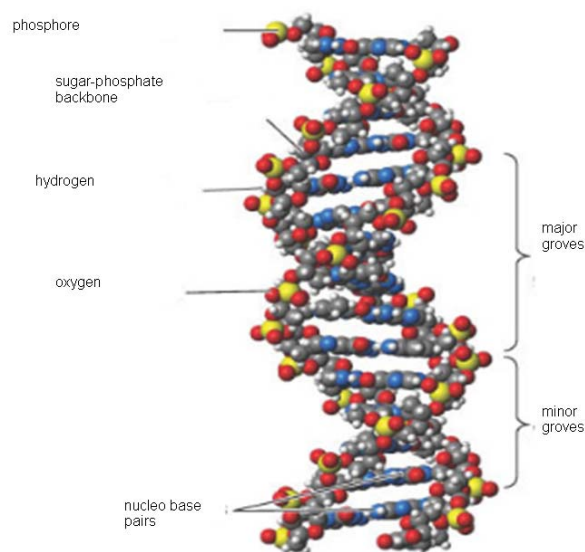

**Fig. 1 - Chemical structure of a segment of DNA molecule (adapted from [6])**

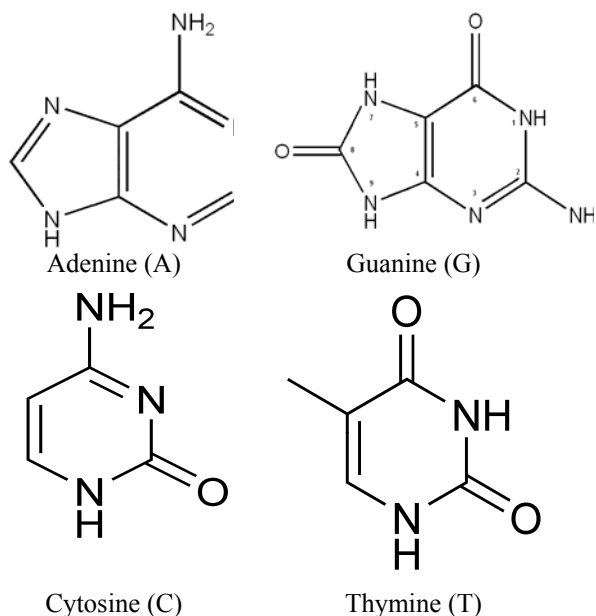

Indeed, this supramolecule exhibits a peculiar double helix structure, consisting of stacked base pairs of molecules arranged as rungs of the ladder. The pairs consist always of adenine with thymine and of guanine with cytosine. The two helix backbones are made of sugar and phosphate groups, joined internally by the ester bonds. The base pairs are linked together by the strong hydrogen bonds. Because the outside groups are phosphates, the DNA macromolecule presents a net negative charge, compensated by sodium ions, which are non-localized counter ions. They can move freely along the macromolecular chain surface [7].

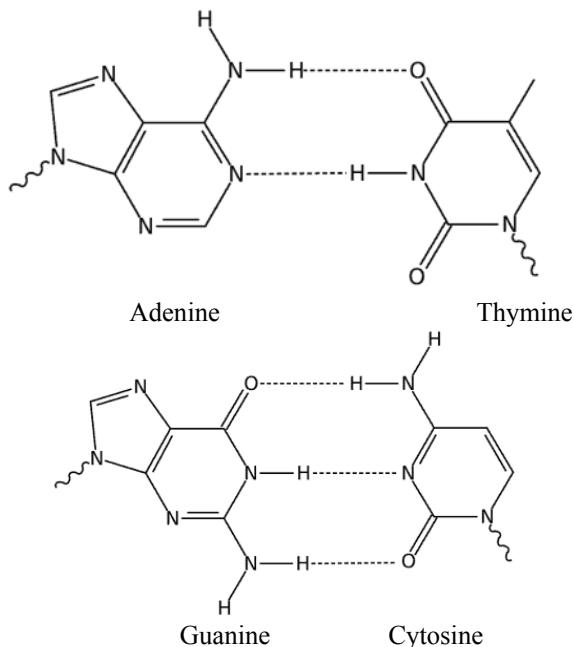

As it was found originally by X Ray studies by Watson and Crick the pitch of the helix is of 3.4 nm, its diameter of 1 nm respectively and the distance between two neighbouring nucleotides of 0.34 nm (cf. Figure 1). In solution these dimensions may be a little different as reported by Mandelkern *et al* [8], ranging from 2.2 to 2.6 nm for the helix radius, 3.3 nm for the pitch, and 0.34 nm for the distance between two nucleotides.

The double stranded helix form major and minor grooves, wide, respectively, of 2.2 nm and 1.2 nm [9]. Their presence is important for the functionalization of DNA as it will be discussed later.

The size of DNA depends on the level of development of a given specie. Usually it is expressed in the number of base pairs (bp) and spans from several tens of bp, as for *Escherichia coli* bacteria (76bp), to 3 000 Mbp for Human DNA [10]. There exist a lot of programs available on internet which transform the base pairs number into molecular mass (Daltons). A base pair has molecular mass of about 660 Da.

One of the important arguments used in favour of biopolymers for replacing the synthetic polymers in photonics and in electronics, and particularly by DNA, is its abundance and renewability. DNA is usually obtained from the waste produced by food processing industry. Thus it can be cheap. In contrary to synthetic polymers, if not protected, biopolymers are biodegradable. Thus their use should permit to decrease the pollution by slowly decomposing synthetic polymers. This is comforted by the present scientific policy related to the humanity problem of creating a sustainable society with durable development, disposing renewable resources and minimising the environment pollution.


Besides the above mentioned advantages, there are other important properties of DNA, which are in favour of its in photonics and in electronics, as it will be shown and discussed later in this paper. It concerns, in particular the versatility, thin film processability and the possibility of tailoring optical and electrical properties by DNA functionalization. Its specific double strand helical structure, with minor and major grooves, provides a large free volume for doping molecules as well as a good protection against photo thermal degradation.

Another potentially very interesting biopolymer is collagen. Its name originates from Greek word *kola* meaning glue. It was indeed used as glue in antic times. This biopolymer is the most abundant in human and animal organisms supramolecule, making *ca* 25 % of all their proteins, *i.e.* 5% of their mass. It plays an important role in assuring connectivity of mammals tissues [11] and in their structuring. Its molecular mass is of *ca* 325 000 Da. A collagen fiber with 1 mm diameter may withstand a 10 kg load.

The collagen molecule is composed of three associated alpha polypeptide chains, as shown in Figure 4, linked by hydrogen bonds between hydroxylysine and l'hydroxyproline and by covalent bonds. An alpha chain is constituted of 1055 amino acids. They may combine in different ways and form a large variety of different collagens. Each of them is characterized by an appropriate structure and exerts a particular role in a given organ. For example collagen I is present in cornea, skin and bones while collagen III can be found in the cardiovascular system.

The building unit of collagen is the tropocollagen. It is a noncentrosymmetric molecule, exhibiting second harmonic generation as observed by several research groups. The length of tropocollagen is of *ca* 280 nm and the diameter of 1.5 nm, respectively. The already mentioned constituent elements amino

acids comprise glycine, proline, hydroxylysine and 4-hydroxyproline (cf. Figure 2). There are several types of molecular chains, which are composed of repetitive sequences of these amino acids. Glycine is repeated throughout the molecule. The carbohydrates are attached to hydroxylysine. The cohesion of tropocollagen is ensured by strong hydrogen bonds between glycine and hydroxyproline (Figure 2).

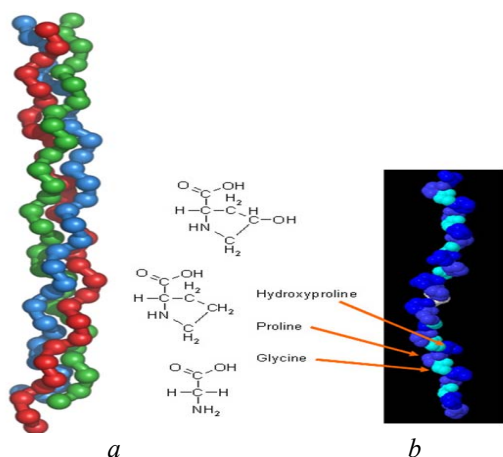

**Fig. 2 - Chemical structure of collagen (a) and of tropocollagen (b)**

The deoxyribonucleic acid exhibits little  $\pi$  electron conjugation which is interesting for application in photonics. It is mainly to the presence of double C=C bands, in nucleobases. Such conjugation is absent in collagen. Therefore to obtain desired properties necessary for practical applications both biopolymers

In this Chapter we review and discuss the results of our recent studies on functionalization, photo-thermal stability of collagen and DNA and collagen based complexes, together with stability in high intensity laser beams.

## 2. Materials

The deoxyribonucleic acid we are using in our studies was purchased at Ogata Photonics Laboratory, Chitose, Hokkaido, Japan. It is obtained from the waste produced in salmon processing [12, 13], particularly from roe and milt. Frozen roe and milt are first grinded. Then the grinded product is homogenized. Then starts the important and difficult process of protein elimination. The homogenized product is treated with enzymes DNA, dissolved in water and decolorized with active carbon. Finally the product is filtered and freeze-dried. The most delicate and difficult step in purification process is the separation of proteins. The final product contains usually *ca* 98 % of DNA and *ca* 2% of proteins ([13]).

Collagen is also obtained from the waste produced in meat processing. It is usually obtained from skin and bones of animals, principally such as beefs and porcs as well as from fish [14, 15]. The collagen used in our study was obtained at University Politehnica of Bucharest from beef skin using an original procedure described in Refs. [16, 17]. DNA is known to denature at around 90 °C, changing its helical structure from double stranded to single stranded [18, 19], limiting in


this way the temperature range of applicability. Also thin film processing and water solubility only limits the possible range of its applications.

Collagen can be irreversibly hydrolyzed giving gelatine, which is largely used in food industry.

## 3. Functionalization

As already mentioned pure DNA and collagen represent a limited interest for applications in, particularly, photonics. They exhibit low  $\pi$  electron conjugation, which is principally present in DNA only owing to the  $\text{--C=C--}$  conjugated bonds in nucleobases.

Pure DNA has a limited potential for applications in photonics. This biopolymer is soluble in water only, a solvent which doesn't belong to the preferred ones in the device fabrication technologies, although some electronic devices containing water were already described [20, 21]. Also a weak  $\pi$  electron conjugation, only in phenyl rings, provides limited hyperpolarizabilities to this compound. Therefore the only possible practical use of this biopolymer in photonics is as an optically inactive material, except if its chirality can be exploited in some ways.

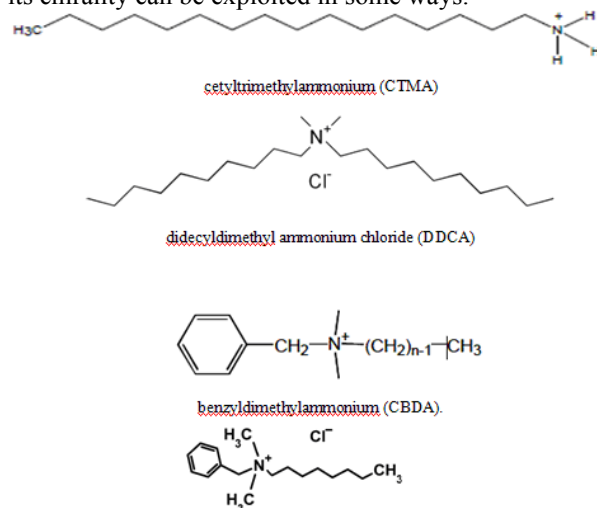


DNA is an anionic polyelectrolyte [22, 23] with  $\text{Na}^+$  ion being a counter ion. Therefore the first possible approach to functionalize is through the electrostatic interaction by substituting  $\text{Na}^+$  by a positively charged molecule, which will be bond to the DNA helix by the electrostatic force, changing in this way its properties. Several approaches were done in this direction. A significant DNA material improvement was obtained by functionalizing it chemically with ionic liquids, as shown by Iijiro & Okahata [24], Okahata [25, 26], Serguev *et al* [27], Kimura *et al* [28], and more particularly by Ogata and coworkers from Chitose Institute of Technology [29-41]. They have shown that the counterion  $\text{Na}^+$  can be substituted by an amphiphilic cation, leading to a more stable compound, soluble in polar organic solvents and generally insoluble in water. They used several cationic surfactants which react with DNA *via* electrostatic forces and they succeeded in making several stable complexes using surfactants such as: cetyltrimethylammonium (CTMA) (Wang *et al* [42] and an aromatic one the benzyldimethylammonium (CBDA) [37] Watanyuki], whose chemical structures are shown in Figure 6. Recently some other surfactants



were proposed, such as aromatic ones: benzalkonium chloride (BA), and a linear amphiphilic one didecylmethyl ammonium chloride (DDCA). The complexes formed with the new surfactants are soluble in a larger number of solvents making possible DNA functionalization with a greater class of molecules.

Figure 3 shows schematically the reaction of a surfactant (with a counterion, usually  $\text{Cl}^-$  or  $\text{ClO}_4^-$ ) with DNA (counterion  $\text{Na}^+$ ). As result of this reaction a stable DNA-surfactant complex is formed, which precipitates in reaction solvent (water) and can be easily recovered. The resulting from the reaction sodium ion forms a salt with the surfactant counterion which remain in water. The DNA surfactant complexes are well stable. Their thermal degradation takes place at around  $230^\circ\text{C}$  ([43-45]).

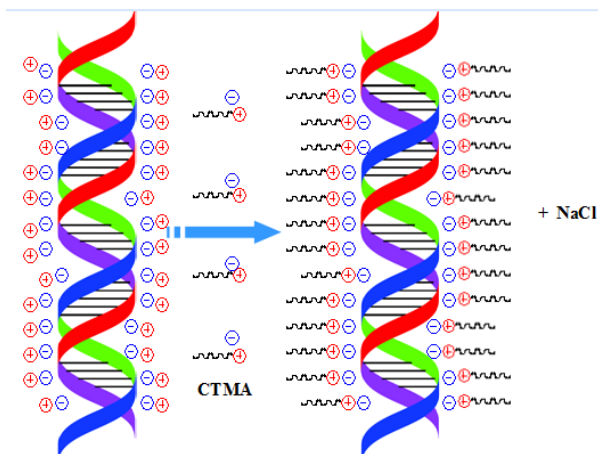


**Fig. 3 - Electrostatic interaction between DNA and surfactant leading to the formation of a stable complex (courtesy of J. G. Grote, UA Air Force Wright Patterson Research Labs, Dayton, OH, USA)**

As already mentioned DNA undergoes a denaturation process when heated to  $90^\circ\text{C}$ . It consists on transformation from double strand to single strand helix. In contrary, the DNA – surfactant complex show a better stability, maintaining its double stranded helical structure to temperatures overpassing  $100^\circ\text{C}$  [13], what is sufficient for majority of practical applications.

Functionalization of DNA with the above cited surfactants does not provide them the required in photonics photosensitivity, as the molecules used show also a little (aromatic surfactants) or none (amphiphilic surfactants)  $\pi$  electron delocalization. Figure 4 compares optical absorption spectra of thin films of DNA with those made of two complexes: All show absorptions around  $260\text{ nm}$ , which are due to conjugated  $\pi$  electrons of nucleobases and of phenyl ring in the case of aromatic surfactants. Therefore it is necessary to functionalize the biopolymer or its complex with a surfactant with a photosensitive molecule. This can be done in three different ways:

1. intercalation,
2. random doping, as in the case of synthetic polymers,
3. doping through molecules inclusion in minor or major grooves,
4. covalent attachment to DNA chains.

Intercalation consists on introduction of a doping molecule between nucleobase pairs stacks, as shown in Figure 4 (a).

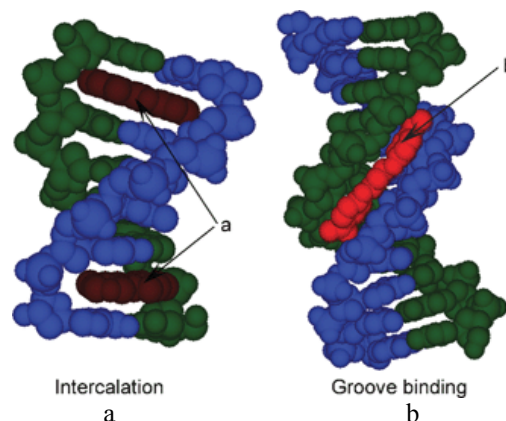


**Fig. 4 - Intercalation (left) and groove binding (right) of chromophores in DNA [49]**

As the space is limited, only small, ring type, flat molecules can intercalate. A large  $\pi$  electron overlap between the doping molecules and the nucleobase pairs is expected in this case.

Recently Pawlik *et al* [46] (see also Refs. [47, 48]) have proposed another intercalation mechanism for DNA – surfactant complexes they proposed to call “semi-intercalation”. In that case the doping molecules are partly inserted between the surfactant molecules for DR1 in DNA – CTMA matrix.

Thus the dopants do not bind directly to the DNA backbone but are separated from, keeping in this way a larger conformational mobility. The Monte Carlo simulation calculations performed using this model allowed to explain the photochromic properties of DNA–CTMA–DR1 complex.

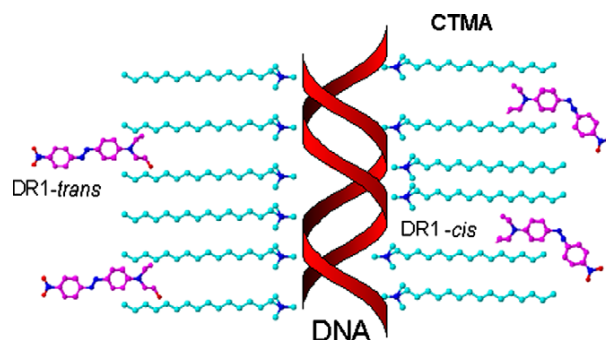


They reproduced accurately the main experimental results of laser dynamic inscription of diffraction gratings in this photochromic material: short response time, low diffraction efficiency, single-exponential kinetics and flat wavelength dependence. It allowed also to explain also the origin of memory effect upon light excitation observed in DNA–CTMA–DR1 complexes.


The simplest way of DNA or DNA – surfactant functionalization is by making solid solutions, as it is frequently done with synthetic polymers, and as it was proposed originally by Havinga and Pelt [50] to improve electroluminescent properties of some organic dyes. This is done in solution, while existence of a

common solvent is required. It is difficult to be done with DNA and collagen as these biopolymers are soluble in water only. The DNA – surfactant complexes are insoluble in water and soluble, depending on surfactant used, in a large variety of solvents. Indeed, lot of different complexes, particularly DNA – surfactant – photosensitive chromophore complexes were successfully made in this way [see e.g. Grote [13], Rau *et al* [51], Derkowska *et al* [52]).

Some, particularly linear molecules, like so called Hoechst molecule 33258 fits into the minor or major grooves of DNA, without a Van der Waals contact.

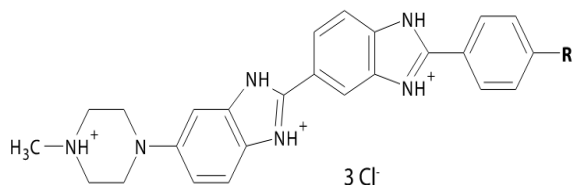

*Hoechst molecule 33258 ( $C_{25}H_{26}N_6R$ ) chloride*

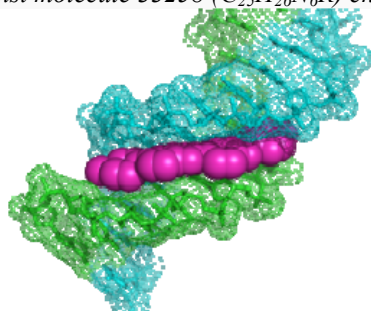

*Binding of Hoechst molecule 33258 ( $C_{25}H_{26}N_6R$ ) chloride to the minor groove of DNA*

This type of molecules, if showing photoluminescence, is used to stain DNA, are important and find large practical applications, particularly in criminology.

There are several attempts to attach covalently the photosensitive molecules to DNA by using different synthetic methodologies. In particular a lot of efforts was done with planar molecules, such as porphyrins through a direct modification of nucleobases [54] or using acyclic linkers [55]. Attempts were also done in replacing nucleobases in the middle of the helix by porphyrin molecules [56] for solar energy conversion [57, 58] as well as in photodynamic therapy applications [59].

Recently Stephenson *et al* [60, 61] reported the synthesis of  $\beta$  - pyrrolic-functionalised porphyrins and their covalent attachment to 2'-deoxyuridine and DNA. The authors observed a better thermal stabilisation of parallel porphyrin-modified triplex-forming oligonucleotide strands, while the anti-parallel duplexes were destabilised.


#### 4. Thin film processing

A lot of practical applications of photonic and electronic materials are expected to be done in thin films.

Therefore the ability of processing of given materials into this form is important. In the present case all discussed here biopolymers: DNA, DNA - chromophore DNA – surfactant, DNA – surfactant –

chromophore as well as collagen and collagen – chromophore. Good optical quality thin films can be obtained by usual solution casting techniques. For DNA – CTMA we use commonly butanol as solvents. But some other, like methanol, ethanol, isopropanol, cyclohexanone and methyl isobutyl ketone can be also used. For complexes with other surfactants more solvents can be used. Thin films of DNA-CTMA complex, obtained by spin coating, were found to be partly ordered, with measured anisotropy of refractive index [62].

Some examples of thin films deposited by spinning on glass substrates are given in Figure 10 (b-c). An AFM picture of collagen thin films, showing the already mentioned fibrillar structure of this biopolymer is shown in Figure 5.

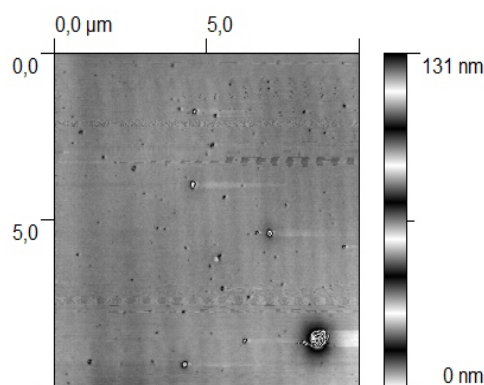

**Fig. 5 - AFM image of the collagen thin films surface. The mentioned fibrillar structure is well seen**

#### 7. Conclusions

In this Chapter we review and discuss the recent work on two biopolymers: collagen and deoxyribonucleic acid in view of their application in photonics. Both are abundant, renewable, biodegradable and nature fabricated macromolecules. They can be obtained from the waste produced in food processing industry. That used in our studies originates from the waste produced in salmon processing industry. Thus they can be cheap and the renewable resources are practically unlimited. It can be used, at least partly, to replace synthetic polymers as matrix for photosensitive molecules, offering an interesting, ecologically friendly, alternative material for applications in photonics and in electronics.

Owing to its peculiar double stranded helical structure DNA offers more than synthetic polymers. Particularly there is a larger free volume offering faster conformational processes, as discussed here, and at the same time a better stability of embedded molecules. Indeed, as shown by described and discussed here the recent photothermal degradation studies performed on a series of DNA based complexes significantly larger first order decay constants for several chromophores embedded in collagen or DNA matrices than when these molecules are dissolved in the commonly used synthetic polymers like the polymethyl methacrylate (PMMA). Also, DNA exhibits a higher optical damage threshold.

DNA can be functionalized with surfactants, leading to a temperature stable material, processable into good optical quality thin films by solution casting techniques. The structure of DNA and the ionic environment it offers changes the physico-chemical properties of embedded active molecules in a favourable way as shown and discussed in this paper. Different doping mechanisms were indicated. The richness of the possible functionalization of DNA gives possibility of obtaining an important class of materials with new properties and new functionalities. They may be cheap, as obtained from the waste produced in the food processing industries and they are environmentally friendly, as already mentioned. As photoactive materials natural chromophores, like anthocyanines, can be, perspectively, used too [63]. We note too that the liquid crystalline phase was also isolated in DNA and investigated [64] as well as in a DNA-surfactant complex [65].

### Acknowledgements

The authors acknowledge the financial support of Romanian Ministry of Education, Research, Youth and Sports, through the UEFISCDI organism, under Contract Number 279/7.10.2011, Code Project PN-II-ID-PCE-2011-3-0505.

### References

1. <http://www.brighthub.com/environment/green-living/articles/107380.aspx>.
2. J. P. Vigneron, J.F. Colomer, N. Vigneron, V. Lousse, Natural layer-by-layer photonic structure in the squamae of *Hoplia coerulea* (Coleoptera, ) *Phys. Rev. E*, 72 (2005), 061904-061906.
3. D. E. Azofeifa, H. J. Arguedas, W. E. Vargas, Optical properties of chitin and chitosan biopolymers with application to structural color analysis, *Opt. Mat.*, 35(2), , 175–183(2012); DOI: <http://dx.doi.org/10.1016/j.optmat.2012.07.024>.
4. J. D. Watson and F. H. C. Crick, Molecular structure of nucleic acids. A structure for deoxyribose nucleic acid, *Nature*, 171, 737-738(1953).
5. F. H. C. Crick and J. D. Watson, The complementary structure of deoxyribonucleic acid. *Proc. Royal Soc. (London)*, 223, 80-96(1954).
6. L. A. Pray, Ph.D. Discovery of DNA structure and function: Watson and Crick, *Nature Education*, *Nature Education*, 1(1) (2008).
7. G. S. Manning, The molecular theory of polyelectrolyte solutions with applications to the electrostatic properties of polynucleotides, *Q. Rev. Biophys.*, 11(2), 179 - 246(1978).
8. M. Mandelkern, J. Elias, D. Eden, D. Crothers The dimensions of DNA in solution. *J Mol Biol.*, 152 (1), 153–61(1981)., doi:10.1016/0022-2836(81)90099-1.
9. H. Clausen-Schaumann, M. Rief, C. Tolksdorf, H. Gaub, Mechanical stability of single DNA molecules. *Biophys J*, 78 (4): 1997–2007(2000), doi:10.1016/S0006-3495(00)76747-6.
10. <http://dwb4.unl.edu/Chem/CHEM869N/CHEM869NLinks/chemistry.about.com/science/chemistry/library/weekly/aa061598a.htm>.
11. <http://fr.wikipedia.org/wiki/Collag%C3%A8ne>.
12. L. Wang, J. Yoshida, N. Ogata, S. Sasaki, and T. Kajiyama, Self-assembled supramolecular films derived from marine deoxyribonucleic acid (DNA)-cationic surfactant complexes: large-scale preparation and optical and thermal properties, *Chem. Mater.* 13 (4), pp. 1273–1281, 2001.
13. J. Grote, Biopolymer materials show promise for electronics and photonics applications, *SPIE newsroom*, DOI 10.1117/2.1200805.1082(2008).
14. M. H. Uriarte-Montoyaa, J. L. Arias-Moscossa, M. Plascencia-Jatomea, H. Santacruz-Ortega, O. Rouzaud-Sández, J. L. Cardenas-Lopez, E. Marquez-Rios, J. M. Ezquerro-Brauer, Jumbo squid (*Dosidicus gigas*) mantle collagen: Extraction, characterization, and potential application in the preparation of chitosan–collagen biofilms, *Bioresource Technology*, 101 4212–4219(2010).
15. L. Wang, Q. Liang, Z. Wang, J. Xu, Y. Liu, H. Ma, Preparation and characterisation of type I and V collagens from the skin of Amur sturgeon (*Acipenser schrenckii*), *Food Chemistry*, 148, 410–414(2014).
16. V. Trandafir, G. Popescu, M. G. Albu, H. Iovu, M. Georgescu, *Bioproduse pe baza de collagen*, Editura Ars Docendi, Bucuresti, 2007, ISBN: 978-973-558-291-3.
17. M. G. Albu, *Collagen gels and matrices for biomedical applications*, Lambert Academic Publishing, Saarbrücken. 2011. ISBN 978-3-8443-3057-1.
18. D. L. Vizard, R. White A and A. T. Ansevin, Comparison of theory to experiment for DNA thermal denaturation, *Nature*, 275, 250–251(1978).
19. J. SantaLucia, Jr., A unified view of polymer, dumbbell, and oligonucleotide DNA nearest-neighbor thermodynamics. *Proc. Natl. Acad. Sci. USA*, 95(4), 1460–1465(1998). doi:10.1073/pnas.95.4.1460. PMID 9465037.
20. R. A. Hayes, B. J. Feenstra, Video-speed electronic paper based on electrowetting. *Nature*, 425, 6956, 383-385(2003).
21. M. Nogi and H. Yano, Transparent Nanocomposites Based on Cellulose Produced by Bacteria Offer Potential Innovation in the Electronics Device Industry. *Adv. Mat.*, 20, 1849-1852(2008).
22. M. C. J. Large, D. T. Croke, W. J. Blau, P. McWilliam, F., Kajzar, EFISH in electrolyte and polyelectrolyte systems, *Mol. Cryst. Liq. Cryst., Sc. & Technol., Section B: Nonl. Opt.*, 12(3), 225–238 (1995).
23. M. C. J. Large, D. T. Croke, W. J. Blau, P. McWilliam, F., Kajzar, Molecular Length Dependent Type Polarizability, in *Nonlinear Optical Properties of Organic Molecules IX*, G. Mohlmann Ed., *Proc. SPIE*, vol. 2852, 36 (1996).
24. K. Ijro, Y. Okahata, A DNA–lipid complex soluble in organic solvents, *J. Chem. Soc., Chem. Commun*, 18, 1339–1341 (1992).
25. Y. Hoshino, H. Nakayama, Y. J. Okahata, Preparations of a RNA-lipid complex film and its physical properties, *Nucleic Acids Res. Suppl.* No. 1, 61–62 (2001).
26. K. Tanaka, Y. J. Okahata, A DNA–Lipid Complex in Organic Media and Formation of an Aligned Cast Film, *J. Am. Chem. Soc.*, 118(44), 10679–10683 (1996).
27. V. G. Sergeev, O. A. Pyshkina, A. V. Lezov, A. B. Mel'nikov, E. I. Ryumtsev, A. B. Zevin. V. A. Kabanov, DNA Complexed with Oppositely Charged Amphiphile in Low-Polar Organic Solvents, *Langmuir*, 15, 4434–4440 (1999).
28. H. Kimura, S. Machida, K. Hone, Y. Okahata, Effect of Lipid Molecules on Twisting Motions of DNA Helix Studied by Fluorescence Polarization Anisotropy, *Polymer J.*, 30, 708–712 (1998).
29. A. Watanuki, J. Yoshida, S. Kobayashi, H. Ikeda, N. Ogata, Optical and photochromic properties of spiropyran-doped marine-biopolymer DNA-surfactant complex films. *Proc. SPIE*, 5724, 234–241 (2005).
30. Y. Kawabe, L. Wang, T. Koyama, S. Horinouchi, N. Ogata, Light amplification in dye doped DNA-surfactant complex films, *Proc. SPIE*, 4106, 369–376 (2000).
31. L. Wang, G. Zhang, S. Horinouchi, J. Yoshida, N. Ogata, Optoelectronic materials derived from salmon deoxyribonucleic acid, *Nonl. Opt.*, 24, 63–68 (2000).
32. Y. Kawabe, L. Wang, S. Horinouchi, N. Ogata, Amplified spontaneous emission from fluorescent dye-doped DNA-surfactant films, *Adv. Mater.* 12, 1281–1283 (2000).
33. T. Koyama, Y. Kawabe, N. Ogata, Electroluminescence as a probe for electrical and optical properties of deoxyribonucleic acid, *Proc. SPIE*, 4464, 248–255 (2002).
34. L. Wang, M. Fukushima, J. Yoshida, N. Ogata, A novel photochromic film materials derived from supramolecules, DNA-surfactant complex: Spiropyran-DNA-CTMA complex,

- Nanotechnology toward theorganic photonics, GooTech Ltd., Chitose-shi, Japan, 379–384 (2002).
35. J. Yoshida, L. Wang, S. Kobayashi, G. Zhang, H. Ikeda, N. Ogata, Optical properties of photochromic-compound-doped marine-biopolymer DNA-surfactant complex films for switching applications, *Proc. SPIE*, 5351, 260 (2004).
  36. L. Wang, K. Ishihara, H. Izumi, M. Wada, G. Zhang, T. Ishikawa, A. Watanabe, S. Horinouchi, N. Ogata, Strongly luminescent rare-earth ion-doped DNA-CTMA complex film and fiber materials, *Proc. SPIE*, 4905, 143–152 (2002).
  37. A. Watanuki, J. Yoshida, S. Kobayashi, H. Ikeda, N. Ogata, Optical and photochromic properties of spiropyran-doped marine-biopolymer DNA-surfactant complex films. *Proc. SPIE*, 5724, 234–241 (2005).
  38. Y. Kawabe, L. Wang, T. Koyama, S. Horinouchi, N. Ogata, Light amplification in dye doped DNA-surfactant complex films, *Proc. SPIE*, 4106, 369–376 (2000).
  39. L. Wang, G. Zhang, S. Horinouchi, J. Yoshida, N. Ogata, Optoelectronic materials derived from salmon deoxyribonucleic acid, *Nonl. Opt.*, 24, 63–68 (2000).
  40. T. Koyama, Y. Kawabe, N. Ogata, Electroluminescence as a probe for electrical and optical properties of deoxyribonucleic acid, *Proc. SPIE*, 4464, 248–255 (2002).
  41. J. Yoshida, L. Wang, S. Kobayashi, G. Zhang, H. Ikeda, N. Ogata, Optical properties of photochromic-compound-doped marine-biopolymer DNA-surfactant complex films for switching applications, *Proc. SPIE*, 5351, 260 (2004).
  42. L. Wang, J. Yoshida, N. Ogata, S. Sasaki, T. Kamiyama, Self-Assembled Supramolecular Films Derived from Marine Deoxyribonucleic Acid (DNA)-Cationic Surfactant Complexes: Large-Scale Preparation and Optical and Thermal Properties, *Chem. Mat.*, 13(4), 1273–1281(2001).
  43. E. Bajer, Modyfikacja DNA dla zastosowań w optyce nieliniowej (Modification of DNA for application in nonlinear optics), Master thesis, Cracow University of Technology, Poland, 2010.
  44. Y. – C. Hung, W. T.-Y. Lin Hsu, Y.-W. Chiu, Y. – S. Wang and L. Fruk, Functional DNA biopolymers and nanocomposite for optoelectronic applications, *Opt. Mat.*, 34, 1208–1213(2012).
  45. J. Nizioł, M. Sniechowski, E. Hebda, M. Jancia, J. Pielichowski, Properties of DNA complexes with new cationic surfactants, *Chem. Chem. Technol.*, 5(4), 397–402(2011).
  46. G. Pawlik, A. C. Mitus, J. Myśliwiec, A. Miniewicz, J. G. Grote, Photochromic dye semi-intercalation into DNA-based polymeric matrix: Computer modelling and experiment, *Chem. Phys. Lett.* 484, 321–323(2010).
  47. G. Pawlik, W. Radosz, A. C. Mitus, J. Myśliwiec, A. Miniewicz, F. Kajzar, I. Rau, Grating inscription in DR1:DNA-CTMA thin films: theory and experiment, *Proc. SPIE*, 8817, 8170D-1-6 (2013).
  48. G. Pawlik, W. Radosz, A. C. Mitus, J. Myśliwiec, A. Miniewicz, F. Kajzar, I. Rau, J. G. Grote, Kinetics of grating inscription in DR1:DNA-CTMA thin film: experiment and semi-intercalation approach, *Proc. SPIE*, 8464, 846404(2012).
  49. [https://www.google.ro/search?q=dna+groove+binding&tbm=isch&tbo=u&source=univ&sa=X&ei=iCDNUsb1OZLioATeYKACA&ved=0CEUQsAQ&biw=911&bih=361#facrc=\\_&imgdii=\\_&imgsrc=OhEsBsXoyD0awM%3A%3BiAY0dgn2AAa0gM%3Bhttp%253A%252F%252Fwww.rsc.org%252F%252F%252F2008%252Fb801433g%252Fb801433gf11.gif%3Bhttp%253A%252F%252Fpubs.rsc.org%252Fen%252Fcontent%252Farticlehtml%252F2008%252Fcs%252Fb801433g%3B331%3B256](https://www.google.ro/search?q=dna+groove+binding&tbm=isch&tbo=u&source=univ&sa=X&ei=iCDNUsb1OZLioATeYKACA&ved=0CEUQsAQ&biw=911&bih=361#facrc=_&imgdii=_&imgsrc=OhEsBsXoyD0awM%3A%3BiAY0dgn2AAa0gM%3Bhttp%253A%252F%252Fwww.rsc.org%252F%252F%252F2008%252Fb801433g%252Fb801433gf11.gif%3Bhttp%253A%252F%252Fpubs.rsc.org%252Fen%252Fcontent%252Farticlehtml%252F2008%252Fcs%252Fb801433g%3B331%3B256)
  50. E. E. Havinga and P. Van Pelt, Electrochromism of organic dyes in polymer matrices, in *Electrochromism of organic dyes in polymer matrices*, B. R. Jennings (Ed.), Plenum Press, New York 1979, pp. 89 – 97.
  51. I. Rau, R. Czaplicki, B. Derkowska, J. G. Grote, F. Kajzar, O. Krupka and B. Sahraoui, Nonlinear Optical Properties of Functionalized DNA-CTMA Complexes, *Nonl. Opt. Quant. Opt.*, 42, 283-324(2011).
  52. B. Derkowska, M. Wojdyla, W. Bala, K. Jaworowicz, M. Karpierz, J.G. Grote, O. Krupka, F. Kajzar and B. Sahraoui, Influence of different peripheral substituents on the nonlinear optical properties of cobalt phthalocyanine core, *J. Appl. Phys.*, 101, (8), 083112(1-8), (2007)
  53. [http://en.wikipedia.org/wiki/File:Structure\\_of\\_Hoechst\\_dyes.svg](http://en.wikipedia.org/wiki/File:Structure_of_Hoechst_dyes.svg).
  54. I. Bouamaied, L.-A. Fendt, D. Hussinger, M. Wiesner, S. Thöni, N. Amiot, E. Stulz, Nucleosides Nucleotides, *Nucleic Acids*, 26, 1533 –1538(2007).
  55. A. Onoda, M. Igarashi, S. Naganawa, K. Sasaki, S. Ariyasu, T. Yamamura, *Bull. Chem. Soc. Jpn.*, 82, 1280 – 1286(2009).
  56. K. Berlin, R. K. Jain, M. D. Simon, C. Richert, A porphyrin embedded in DNA, *J. Org. Chem.*, 63, 1527 –1535(1998).
  57. W. M. Campbell, K. W. Jolley, P. Wagner, K. Wagner, P. J. Walsh, K. C. Gordon, L. Schmidt-Mende, M. K. Nazeeruddin, Q. Wang, M. Gratzel, D. L. Officer, Highly efficient porphyrin sensitizers for dye-sensitized solar cells, *J. Phys. Chem. C*, 111, 11760 –11762(2007).
  58. W. M. Campbell, A. K. Burrell, D. L. Officer, K. W. Jolley, Porphyrins as light harvesters in the dye-sensitized TiO<sub>2</sub> solar cell, *Coord. Chem. Rev.*, 248, 1363 –1379(2004).
  59. L. M. Moreira, F. V. dos Santos, J. P. Lyon, M. Maftoun-Costa, C. Pacheco-Soares, N. S. da Silva, Photodynamic therapy: porphyrins and phthalocyanines as photosensitizers, *Aust. J. Chem.*, 61, 741 –754(2008).
  60. A. W. I. Stephenson, N. Bomholt, A. C. Partridge, V. V. Filichev, Significantly Enhanced DNA Thermal Stability Resulting from Porphyrin H-Aggregate Formation in the Minor Groove of the Duplex, *Chem. Bio. Chem.*, 11, 1833 – 1839(2010); DOI: 10.1002/cbic.201000326.
  61. A. W. I. Stephenson, A. C. Partridge, V. V. Filichev, Synthesis of b-Pyrrolic-Modified Porphyrins and Their Incorporation into DNA, *Chem. Eur. J.*, 17, 6227 – 6238(2011); DOI: 10.1002/chem.201003200.
  62. A. Samoc, M. Samoc, J. G. Grote, A. Miniewicz and B. Luther-Davies, Optical properties of deoxyribonucleic acid (DNA) polymer host, *Proc. SPIE*, 6401, 6401-1-6 (2006).
  63. I. Iosub, F. Kajzar, M. Makowska-Janusik, A. Meghea, A. Tane A. and I. Rau, Electronic structure and optical properties of some anthocyanins extracted from grapes, *Opt. Mat.*, 34(10), 1644 1650(2012).
  64. H. Mojzisova, J. Olesiak, M. Zielinski, K. Matczyszyn, D. Chauvat and J. Zyss J., Polarization-Sensitive Two-Photon Microscopy Study of the Organization of Liquid- Crystalline DNA, *Biophys. J.* 97, 2348-2357 (2009).
  65. N. Ogata and K. Yamaoka, DNA-lipid hybrid films derived from chiral lipids, *Polymer J.*, 40(3), 186-191(2008).