

E. Arkis, H. Cetinkaya, I. Kurtulus, U. Ulucan,
A. Aytac, B. Balci, F. Colak, E. Topagac German,
G. Kutluay, B. Can Dilhan, D. Balkose,
G. Zaikov, Kh. Abzalidinov

CHARACTERIZATION OF A PEARLESCENT BIAXIALY ORIENTED MULTILAYER POLYPROPYLENE FILM. PART 1

Keywords: pearlescent film, BOPP, x-ray diffraction, SEM, AFM.

The morphology, composition and properties of a commercial pearlescent and multilayer BOPP film were determined in the present study. The film was polypropylene and it was biaxially oriented as shown by FTIR spectroscopy and X-ray diffraction. FTIR spectroscopy indicated carbonate ions, EDX analysis indicated the presence of Ca element, X-ray diffraction showed the presence of calcite. The 30 μm film consisted of a core layer filled with calcite and 4 μm thick upper and lower layers without any filler and from different polymers. There were long air cavities in the core layer with aspect ratios of 23 and 19 in machine and transverse directions making the film pearlescent. The surfaces of the film were very smooth and had surface roughness in the range of 3.052 nm and 11.261 nm as determined by AFM. The film melted at 163.6 °C, had 51 % crystallinity and had 6.3 nm polymer crystals when heated at 10 °C/min rate.

Ключевые слова: перламутровая пленка, БОПП, рентгеноструктурный анализ, СЭМ, АСМ.

В настоящей работе определены морфология, состав и свойства промышленной перламутровой, многослойной пленки БОПП. Исследована полипропиленовая биаксиально-ориентированная пленка, что было показано методом ИК-спектроскопии и рентгеноструктурным анализом. Методом ИК-спектроскопии обнаружены карбонат-ионы, анализ данных EDX указывает на присутствие Ca, рентгеноструктурный анализ показал наличие кальцита. Пленка толщиной 30 мкм состоит из основного слоя, наполненного кальцитом, а также ненаполненных верхнего и нижнего слоев толщиной 4 мкм, содержащих различные полимеры. В основном слое пленки обнаружены длинные воздушные полости с соотношениями сторон 23:19 в, соответственно, продольном и поперечном направлениях, придающие пленке перламутровый оттенок. Пленки имели очень гладкую поверхность с шероховатостью в диапазоне от 3,052 нм до 11,261 нм, что показано методом АСМ. Температура плавления пленки - 163,6 °C, степень кристалличности - 51%, размеры полимерных кристаллов - 6,3 нм при нагревании со скоростью 10 °C/мин.

Introduction

Polypropylene (PP) is one of the most preferred polymer in food packing, protective coating and printing applications with its high stiffness, high temperature resistance, good chemical resistance, lower moisture transmission rate and high mechanical stress properties [1-4]. The polypropylene film that is stretched in both machine direction (MD) and across machine (transvers) direction to improve mechanical properties is called biaxially oriented polypropylene (BOPP). BOPP is widely used in packaging and in a variety of other applications due to their great potential in terms of barrier properties, brilliance, dimensional stability and processability [2]. Different fillers such as talc and calcium carbonate and pigments may be added to BOPP films in order to improve its optical properties and provide a pearly aesthetic look [5, 6]. Thus flexible packaging companies are willing to use pearl films for their inexpensive prices, good decoration, and excellent performance. Generally, because they have a certain pearl effect, they are often used in cold drink packaging such as: ice cream, heat seal label, sweet food, biscuits, and local flavor snack packaging [1].

Mineral particles, such as calcium carbonate and talc powders, are widely used in biaxially oriented films, which are also called cavitated and pearlized structures. Pearled film is based on orientation process, where the interface around the particles is stretched forming small cavities in the polymer structure. The foam extent of the film is low but the film becomes

highly opaque because of inter scratches [4, 7, 8]. Pearl film is a kind of BOPP film by adding pearl pigments into plastic particles and through biaxial stretch heat setting. A typical pearl film is BOPP pearl film produced by A/B/A layer co-extruded biaxial stretch [9]. Three layer films are coextruded where the surface is optimized in order to attain good printability. In fact, the more pigment is in the system the more light is scattered outward, making the system appear opaque and white [10]. Calcium carbonate particles having 0.7-3 μm size are often used in producing micro porous films [11].

The surface morphology of BOPP film could be investigated by atomic force microscopy. The polymer film is characterized by a nanometer-scale, fiberlike network structure, which reflects the drawing process used during the fabrication of the film. the residual effects of the first stretching of the film surface can provide information on the way in which morphological development of the BOPP occurs [12, 13].

The aim of the present study is characterization of a commercial pearlescent BOPP film by advanced analytical techniques. The functional groups, crystal structure, morphology and surface roughness were investigated.

Experimental

Materials

The pearlescent films that were kindly supplied by BAK Ambalaj Turkey were produced in their plant

in Izmir. They were kindly supplied in form of A4 sized sheets with 30 μm thickness.

Methods

The functional groups in pearlescent film were determined by infrared (IR spectroscopy). IRPrestige-21 FT-IR 8400S by Shimadzu was used to obtain FTIR spectrum of the film by transmission technique. The DRIFT FTIR spectra of the both surfaces of the film were obtained in Digilab Excalibur FTIR spectrophotometer using Harricks Praying Mantis attachment.

Crystal structure of the films were determined by x-ray diffraction using Phillips X'Pert Pro diffractometer system. Cu K α radiation was used and a scan rate of $2^\circ/\text{min}$ was applied.

SEM micrographs of upper and lower surfaces and cross section of gold coated Pearlescent BOPP films were taken by a FEI Quanta 250 FEG type scanning electron microscope. Chemical composition of the film surface was determined by EDX analysis using the same instrument.

AFM (Nanoscope IV) and silicon tip was used to obtain surface morphology and roughness of the film. 1 Ohm Silicon tip has coating: front side: none, back side: 50 \pm 10nm Al. Cantilever properties are T: 3.6-5.6 μm , L: 140-180 μm , k: 12-103 N/m, fo: 330-359 kHz, W: 48-52 μm . To achieve surface properties of pearlescent BOPP film, it was cut in 1x1 cm size, then it was put in sample holder in AFM. USRS 99-010, AS 01158-060 serial no OD57C-3930 standard was used in reflection mode. For the reflection spectrum, a black CD was placed at back of the film.

Results and Discussion

FTIR spectroscopy

Figure 1a shows the pearlescent BOPP film FTIR spectrum taken by the transmission method. The peaks between 2950 and 2800 cm^{-1} correspond to the various aliphatic CH stretching modes.

The peaks near 1450 cm^{-1} and 1380 cm^{-1} are the CH_2 and CH_3 deformation bands, respectively [14]. The other peaks below 1400 cm^{-1} are the well-known "fingerprint" of isotactic PP. The peak at around 1500 cm^{-1} of pearlescent BOPP film is wide which is caused existence of calcite. The reason of the increase of the peaks around this region is calcite. The bands at ~ 1420 , ~ 874 and ~ 712 cm^{-1} could be attributed to vibrations of CO_3 group of calcite [15].

The DRIFT FTIR spectra of the both surfaces of the film are seen in Figure 1b. The peak around 3000 cm^{-1} for back surface is similar to previous result but for front surface, peak is very small. The spectrum of the surfaces of the pearlescent film was very different from the transmission spectrum, indicating they were made out of a different polymer. PVdC and acrylic coatings were used for making the pearlescent film heat sealable and printable. However without further characterizations it was not possible to identify the polymer surfaces of the film.

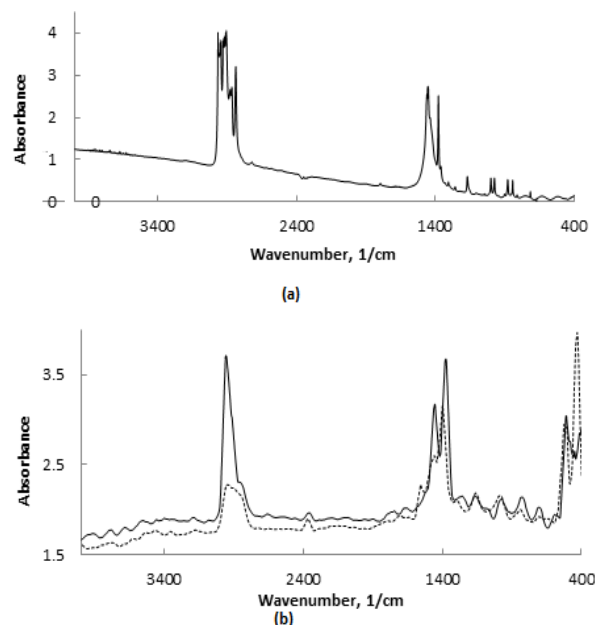


Fig. 1 – a) DRIFT FTIR spectra of front (dotted line) and back (continuous line) surfaces of the film, b) transmission spectrum

X-ray diffraction

In Figure 2 X-ray diffraction diagram of the film in $5-35^\circ$ 2θ range is seen. The maximum reflection points of biaxially orientes isotactic polypropylene were observed at 14.2° (110); 17° (040); 18.85° (130); (111) 21.4° ; (-131) 21.8° 2θ values in the figure [16].

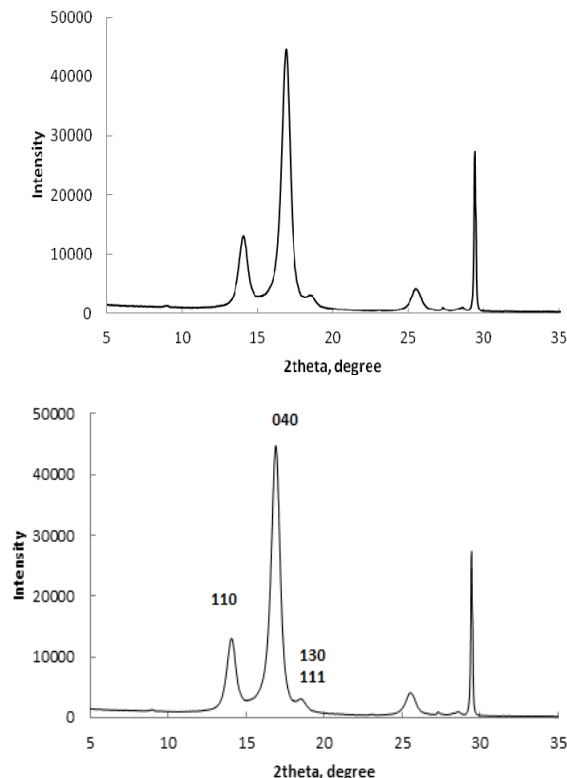


Fig. 2 - X-ray diffraction diagram of the film in $5-35^\circ$ 2θ range

The sharp peak at 29.4° 2θ value can be attributed to 104 planes of calcite. The X-ray diffraction

diagram of the film in 35- 65° 2 theta values is seen in Figure 3. Observed peaks at 36.03, 39.4, 43.2, 47.2, 47.4, 47.6, 48.5° 2theta values are very close to peaks of calcite reported in JCPDS Card Index File, Card 5-5868 [17], which are two theta values of 36.03, 39.4, 43.2, 47.2, 47.5, 48.6. Thus the presence of calcite was also confirmed by x-ray diffraction.

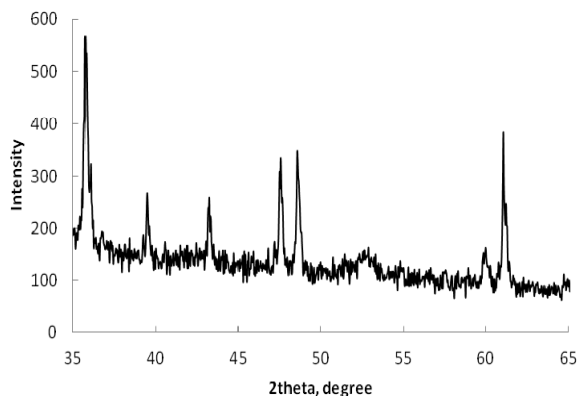


Fig. 3 - X-ray diffraction diagram of the film in 35-65° 2theta range

SEM and EDX

The SEM micrographs of the cross sections of the film in machine and transverse direction are seen in Figure 4.

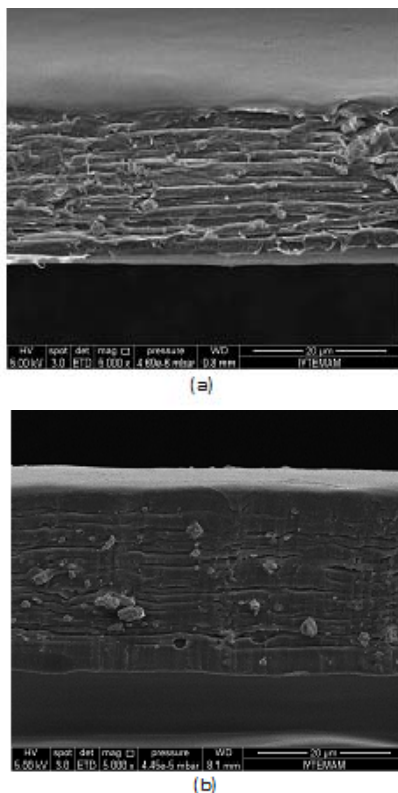


Fig. 4 - SEM micrographs of the cross sections of the film in a) Machine direction, b) Transverse direction

The film has a three layer structure. The top and bottom surface layers which had 4μm thickness do not have any solid particles. FTIR analysis had indicated that the two surfaces were made out of two

different polymers other than the core layer. The SEM micrographs of the surfaces indicated that they were very smooth. The core layer with 22 μm thickness had a stratified structure. There were holes having very high aspect ratio created by the 0.8-3 μm sized particles and the orientation process. The dimensions of the pores in machine direction are length 16.4 ± 6.2 μm and width 0.7 ± 0.3 μm, in transverse direction are length 9.14 ± 3.99 μm and width 0.47 ± 0.5 μm. Mean aspect ratios (length/width) of pores observed in Figure 4a and Figure 4b are 23 and 19 respectively.

The EDX analysis of the surface of the filler particles indicated that they consisted of Ca, C and O elements. They had a composition similar to CaCO_3 which had 40% Ca, 12% C and 48% O. EDX analysis of the particles showed that the particles had 42.8 ± 1.6 % Ca, 22.3 ± 3.73 % C and 34.9 ± 5.2 % O. The particles were calcite and they were coated by a compound which was rich in C.

AFM study

Typical images of the surface of the perleascent film in two and three dimensions are seen in Figure 5. The surface consists of spherical particles. No network structure was observed as indicated by previous studies for 8:1 draw ratio, indicating the draw ratio of the pearleascent film in machine and transverse direction were close to each other.

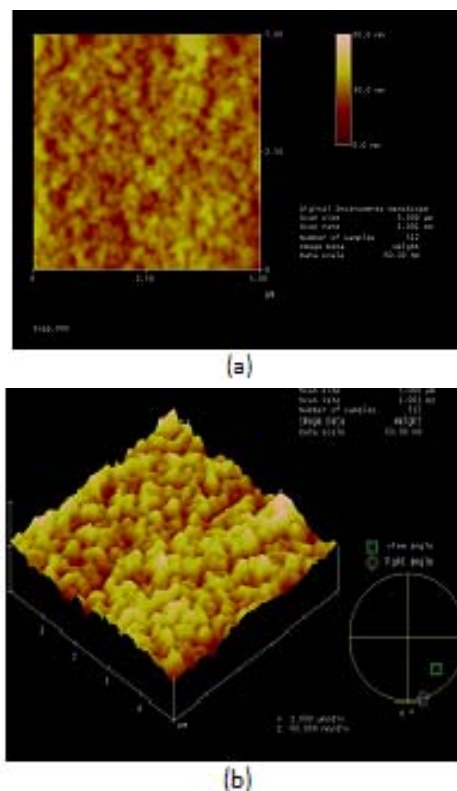


Fig. 5 - AFM micrographs of the surface of the perleascent films a. Two dimensional b. Three dimensional appearance

The surface roughness of the films were determined in three different regions and reported in Table 1. The rootmean square roughness (Rms) was between 3.052 and 11.261nm and average roughness

(Ra) was in the range 2.330-7.326 nm. This low roughness values indicated that the surface of the pearlescent films was very smooth.

Table 1 - Image Statistics of Pearlescent BOPP Films at three different regions

Scan size, $\mu\text{m} \times \mu\text{m}$	5x5	5x5	1x1
Z range, nm	38.155	113.93	21.031
Raw mean, nm	25.591	53.191	-37.563
Rms (Rq), nm	4.861	11.261	3.052
Ra, nm	3.821	7.326	2.330
Srf. Area, μm^2	25.057	25.121	1.003

DSC analysis

DSC analysis was used to determine melting point, melting heat and crystallinity, the crystallite size and activation energy of the melting process. The DSC curves of the sample heated at different rates are seen in Figure 6. A shoulder corresponding to the melting of small crystallites was observed at all heating rates. This shoulder was also observed for biaxial oriented polypropylene by previous investigators [18]. The melting temperature shifts to higher temperatures as the rate of heating was increased. Table 2 shows enthalpy of melting, melting temperature and crystallinity determined at different rates of heating of the film.

The degree of crystallinity (X_c) of the samples from DSC melting peaks were determined using Equation 1.

$$X_c(\%) = \frac{\Delta H_m}{w\Delta H_f^0} \times 100 \quad (1)$$

Where ΔH_m is the melting enthalpy of the samples (J/g) and ΔH_f^0 is the heat of the fusion of PP at 100% crystallinity, correspondent to 207 J.g^{-1} [18]. The crystallinity of the film also increases with the rate of heating.

Table 2 - Enthalpy of melting, melting temperature and crystallinity determined by DSC

B, °C/min	ΔH_m , J/g	T_m , °C	Crystallinity, %	L_c , nm
5	87.63	162.9	48	6.1
10	93.75	163.6	51	6.3
15	129.07	164.2	60	6.5

The Thompson–Gibbs equation predicts a linear relationship between T_m and the reciprocal of crystal thickness.

$$T_m = T_m^0 \left(1 - \frac{2\sigma}{L_c \rho_c \Delta H_f^0} \right) \quad (2)$$

Where σ is the fold surface free energy, T_m^0 is the equilibrium melting temperature, ρ_c is the crystal phase density of pp, ΔH_f^0 is the heat of the fusion of PP

at 100% crystallinity, correspondent to 207 J.g^{-1} [19], and L_c is the thickness of the lamellar crystals. T_m^0 is 459.1 K [20], ρ_c is 946 kg/m^3 [21] and σ is 30.1 mN/m [22]. The crystal thickness values determined by using the melting temperature for different heating rates are reported in Table 2. They were in the range of 6.1 to 6.5 nm.

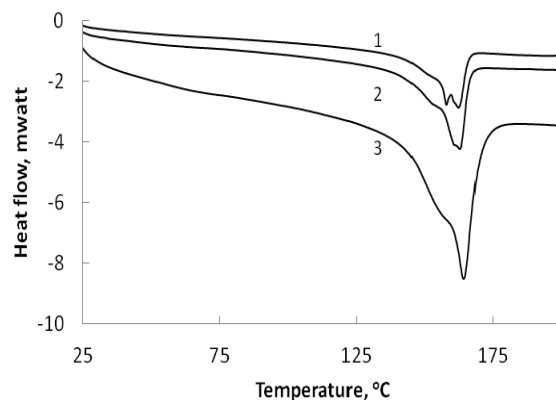


Fig. 6 - DSC curves of the film at 1. 5oC/min, 2.10oC/min, 3. 15oC/min heating rates

Conclusion

A pearlescent packing material supplied by BAK ambalaj Turkey was characterized for obtaining information about its properties for its application fields and its recycle in industry. The advanced characterization techniques such as FTIR spectroscopy, x-ray diffraction, SEM, EDX, AFM and DSC were used for this purpose. The bulk film was polypropylene and it was biaxially oriented as shown by FTIR spectroscopy and X-ray diffraction respectively. FTIR spectroscopy indicated presence of carbonate ions, the presence of Ca element was indicated by EDX analysis. X-ray diffraction showed the presence of calcite. The $30 \mu\text{m}$ film consisted of a core layer of polypropylene filled with calcite and $4 \mu\text{m}$ thick upper and lower layers without any filler were from different polymers. There were long air cavities in the core layer with aspect ratios of 23 and 19 in machine and transverse directions making the film pearlescent. The surfaces of the film were very smooth and had a surface roughness in the range of 3.052 and 11.261 nm as determined by AFM. The film melted at 163.6 oC had 51 % crystallinity and had 6.3 nm polymer crystals for 10 oC/min heating rate.

Acknowledgement

The authors thanks to Bak Ambalaj Turkey for providing the pearlescent films for this study.

References

1. Nie H. .Y, Walzak M. J., McIntyre N. S., Atomic force Microscope Study of Biaxially Oriented Films, Journal of Materials Engineering and Performance, 2009, 13 (4) 4511-460.
2. Introduction of BOPP Film <http://decribopp.wordpress.com> (2013).
3. Longo C., Savaris M., Zeni M., Brandalise R. N., Grisa A.M.C., Degradation Study of Polypropylene and

- Bioriented Polypropylene in the Environment. Materials Research, 2011, 14 (4) 442-48.
4. Raukula J. I., A New Technology to Manufacture Polypropylene Foam Sheet and Biaxially Oriented Foam Film; Thesis, Technical Research Centre of Finland (1998).
 5. Ulku S., Balkose D., Arkis E., Sipahioglu, M., A study of chemical and physical changes during biaxially oriented polypropylene film production, Journal of Polymer Engineering, 2003, 23, 437-456,
 6. Kalapat N. and Amornsakchai T., Surface modification of biaxially oriented poly-propylene (BOPP) film using acrylic acid-corona treatment: Part I. Properties and characterization of treated films, Surface and Coating Technology, 2012, 207, 594-601.
 7. Nago, S. and Mizutani, Y., Microporous Polypropylene Sheets Containing CaCO₃ Filler: Effects of Stretching Ratio and Removing CaCO₃ Filler Journal of Applied Polymer Science, 1998, 68, 1543-1553
 8. Opaque polymeric films and processes making the same US patent 6183856B1, 2001
 9. Koleske JV, Paint and Coating Testing Manual, 14th ed., the Gardner-Sward Ed., Philadelphia, PA: ASTM, 1995.
 10. http://www.plastemart.com/upload/literature/246_art_bopp_in_foodpack.asp (2014).
 11. Biswas J., Kim H., Lee B.H., Choe S., Air-hole properties of calcite-filled polypropylene copolymer films. 2008 Journal of Applied Polymer Science, 109, 1420-1430
 12. Nie H.-Y., Walzak M.J., McIntyre N.S. Atomic Force Microscopy Study of Biaxially-Oriented Polypropylene Films JMEPEG, 2004, 13, 451-460
 13. Nie H.-Y., Walzak M.J., McIntyre N.S. Draw-ratio-dependent morphology of biaxially oriented polypropylene films as determined by atomic force microscopy Polymer, 2000, 41, 2213-2218
 14. Izer A., Kahyaoglu T. N., Balkose D., Valcium Soap Lubricants, Science Journal of Volgograd State University, 10, 1, 16-25
 15. Chen J., Xiang L, Controllable synthesis of calcium carbonate polymorphs at different temperatures, Powder Technology, 2009, 189, 64 – 69.
 16. Diez, F. J., Alvarino, C., Lopez, J., Ramirez, C. Abad, M. J., Cano, J., Garcia-Garabal, S. and Barral, L., "Influence of the Stretching in the Crystallinity of Biaxially Oriented Polypropylene (BOPP) Films," Journal of Thermal Analysis and Calorimetry, 2005, 81, pp. 21-25.
 17. Data from JCPDS Card Index File, Card 5-5868
 18. Yang W., Li Z.-M., Xie B.-H., Feng J.-M., Shi W., Yang M.-B. Stress-Induced Crystallization of Biaxially Oriented Polypropylene Journal of Applied Polymer Science, 2003, 89, 686-690
 19. Bu H.S., Cheng S.Z.D., Wunderlich B. Addendum to the thermal properties of polypropylene. Die Makromolekulare Chemie Rapid Communications 1988, 89(2), 75-77
 20. Yamada K., Hikosaka M., Toda A., Yamazaki S., Tagashira K. Equilibrium melting temperature of isotactic polypropylene with high tacticity: 1. Determination by differential scanning calorimetry Macromolecules, 2003, 36, 4790-4801
 21. <http://en.wikipedia.org/wiki/Polypropylene>
 22. <http://www.surface-tension.de/solid-surface-energy.htm>

© **E. Arkis** - PhD, специалист, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **H. Cetinkaya** – студент PhD, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **I. Kurtulus** – студент PhD, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **U. Ulucan** – студент PhD, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **A. Aytac** – студент магистратуры, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **B. Balci** – студент магистратуры, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **F. Colak** – студент магистратуры, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **E. Topagac Germen** – студент магистратуры, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **G. Kutluay** – студент магистратуры, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **B. Can Dilhan** – студент старшего курса бакалавриата, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **D. Balkose** – профессор, Технологический Институт Измира, кафедра химической технологии, Измир, Турция, **G. Zaikov** – доктор химических наук, профессор кафедры технологии пластических масс, Казанский национальный исследовательский технологический университет, Россия, **Kh. Abzaldinov** – кандидат химических наук, доцент кафедры технологии пластических масс, Казанский национальный исследовательский технологический университет, Россия, ov_stoyanov@mail.ru.

© **E. Arkis** - PhD, specialist, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **H. Cetinkaya** – the student, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **I. Kurtulus** – the student, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **U. Ulucan** – the student, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **A. Aytac** – master, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **B. Balci** – master, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **F. Colak** – master, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **E. Topagac Germen** – master, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **G. Kutluay** – master, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **B. Can Dilhan** – the student, the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **D. Balkose** – Prof., the Technological Institute of Izmir, the department of the chemical technology, Izmir, Turkey, **G. Zaikov** – Prof., KNRTU, **Kh. Abzaldinov** - associate professor, KNRTU, ov_stoyanov@mail.ru.